



## Modification of Spectral Properties of Polystyrene / Diethyl phthalate in Different Solutions

Esam A. Tawfiq<sup>1\*</sup>, Ghada M. Kamil<sup>2</sup>

<sup>1</sup>Department of Applied Science, Branch of Applied Physics, University of Technology, Baghdad, Iraq

<sup>2</sup>Department of Applied Science, Branch of Applied Chemistry, University of Technology, Baghdad, Iraq

### Abstract:

The influence of Diethyl phthalate (DEP) on the optical characteristics of polystyrene solutions in the range between 200 to 400 nm at solvents of different polarities; chloroform, cyclohexane, dichloromethane, and tetrahydrofuran have been recorded. The experimental results showed that the behavior of the photophysical processes of polymer solutions depends on the nature of its environment. The intensity of the absorption and fluorescence spectra depends on the interactions between solvent-solute molecules. The experimental results indicate that the maximum most absorbance bands occur around 262 nm, which depends on the concentration of the quencher. The results did not determine any change in the positions of the most absorption bands. Fluorescence spectra of the polystyrene were measured in chloroform, cyclohexane, dichloromethane, and tetrahydrofuran diluted solutions at room temperature. Fluorescence emission spectra were characterized by one broad main band centered at 295 nm in chloroform and 305 nm in tetrahydrofuran and the emission intensity is dramatically reduced due to strong fluorescence quenching. In cyclohexane and dichloromethane fluorescence spectra of PS/DEP have two bands monomer and excimer emissions at 295 and 328 nm respectively. The presence of DEP quenches the fluorescence and excimer. The excimer emission is more intense. The results showed that the use of different solvents caused a change in the behavior of the fluorescence emission.

**Keywords:** Polystyrene, Diethylphthalate, absorption, fluorescence emission, Fluorescence quenching, excimer emission.

### تعديل الخصائص الطيفية لـ البوليستيرين / ثنائي إيثيل الفثالات في محاليل مختلفة

عصام أحمد توفيق<sup>1\*</sup>، غادة مهدي كامل<sup>2</sup>

<sup>1</sup>قسم العلوم التطبيقية، فرع الفيزياء التطبيقية، الجامعة التكنولوجية، بغداد، العراق

<sup>2</sup>قسم العلوم التطبيقية، فرع الكيمياء التطبيقية، الجامعة التكنولوجية، بغداد، العراق

### الخلاصة


في هذا البحث سجلنا تأثير الملدن ثنائي إيثيل الفثالات على الخصائص الطيفية لمحاليل البوليستيرين في نطاق يتراوح بين 200 إلى 400 نانومتر في مذيبات مختلفة القطبية: - كلوروفورم، سيكلوهكسان، ثنائي كلورو ميثان تتراهدريدوروفوران. أظهرت النتائج التجريبية أن سلوك العمليات الضوئية لمحاليل البوليمر يعتمد على طبيعة الظروف المحيطة بالبوليمر. تشير النتائج، أن حزم الامتصاص القصوى حوالي 262 نانومتر تعتمد على تركيز الملدن (المخمد). بالإضافة إلى ذلك، لاحظنا أن أطراف الامتصاص لا تعاني من

\*Email: esamtawfiq123@gmail.com

أيأزاحة في موقعه. تم قياس أطيايف انبعاث الفلورة للبوليسترين في محاليل الكلوروفورم ، السيكلو هكسان ، داي كلورو ميثان و نيتراهيديروفوران المخففة في درجة حرارة الغرفة. تميزت أطيايف الابعاث بنطاق رئيسي واسع واحد متمركز عند 295 نانوميتر في الكلوروفورم و 305 نانوميتر في رباعي هيدروفوران . انخفضت كثافة الانبعاث بشكل كبير بسبب إخماد الفلورة القوي. في مذيب سيكلو هكسان وثنائي كلورو ميثان أطيايف الفلورة لديها اثنين من نطاقات انبعاث المونومر وانبعاثات الاكسايمر في 295 و 328 نانوميتر على التوالي . وجود الملدن DEP يخدم انبعاث الفلورة والاكسايمر الاعلى شدة. وأظهرت النتائج أن استخدام المذيبات المختلفة تسبب في تغيير في سلوك انبعاث الفلورة

## 1. Introduction

Electronically excited molecules lose their energy in different ways; radiative emission from the first excited state is identical to normal fluorescence and non-radiative transitions appear during many mechanisms. Internal conversion(IC) which cause the molecule to return to the vibration levels with lower energy (energy dissipates in the form of heat). Intersystem crossing (ISC) the molecule shift to the triplet excited state  $3M^*$ . [1-3]. The energy of the excited molecule may transfer to a neighboring molecule (quencher molecule). Generally, energy transfer takes place through to the following equations [4].



Quenching processes occur by electron transfer or energy transfer. In each case, the energy of the excited state is deactivated due to the presence of the quencher [5]. The quenching of fluorescence emission happens by dynamic or static quenching. The first process obtains from interactive collisions between fluorophore and quencher through the lifetime of the excited molecule. This method is determined throughout the transfer of energy from the molecule among the excited state to a different molecule within the ground state. This method is the collision between two molecules the donor molecule and the acceptor, that depends on the temperature and viscosity [6-10].

The quantum efficiency of the fluorescence emission  $\phi_F^0$  within the absence of a quencher is given by [11, 12]:

$$\phi_F^0 = \frac{k_f}{k_f + k_{ic} + k_{isc}} \quad (3)$$

Where  $k_f, k_{ic}$ , and  $k_{isc}$  are the rate constants for fluorescence, internal conversion, and intersystem crossing respectively. The quantum efficiency of the fluorescence emission  $\phi_F$  in the presence of quencher [Q] is given by:

$$\phi_F = \frac{k_f}{k_f + k_{ic} + k_{isc} + k_q[Q]} \quad (4)$$

Where  $k_q$  represents the quenching rate constant of the quencher. The ratio of equations 3 and 4 is:

$$\frac{\phi_F^0}{\phi_F} = \frac{t_o}{t} = \frac{I_o}{I} = 1 + k_q t_o [Q] \quad (5)$$

$$\text{since } k_q = \frac{k_{sv}}{t_o}$$

$$\frac{\phi_F^0}{\phi_F} = 1 + k_{sv}[Q] \quad (6)$$

Where,  $I_o$  is the intensity of sathe mple without quencher,  $t_o$  fluorescence lifetime,  $K_{sv}$  is the Stern-Volmer constant for quenching and  $[Q]$  is the molar concentration for a quencher. The parameter  $(\frac{\phi_F^0}{\phi_F} - 1)$  increases linearly with  $[Q]$ , in this situation the  $k_q$  can be obtained by the (initial) slope of a linear Stern.

In this paper, we concentrate on describing the absorption and fluorescence spectra of polystyrene solutions by addition of different molecular concentrations of the quencher Diethyl phthalate (DEP) with different solvents at room temperature.

## 2. Experimental


Polystyrene has been supplied from (HiMedia ) company. All samples were examined using solvents chloroform, cyclohexane, dichloromethane and tetrahydrofuran. The chloroform and tetrahydrofuran we got by the Scharlau company with 99 and 99.8% purity respectively, cyclohexane solvent was produced from Merck company with 99.9% purity, dichloromethane (DCM) by GC

Company from the United Kingdom with 99.8% purity. These solvents were chosen as a result of they have absorption bands far away from the absorption bands of the samples. All absorption spectra were carried out at room temperature using UV-Vis 160 spectrophotometer (Shimadzu, Japan). Emission spectra were recorded on Shimadzu RF-5301PC Shimadzu Fluorescence Spectrophotometer. In this research, we used the viscosity method to calculate the average molecular weight of polystyrene which is equal to  $1.159 \times 10^5$  g/mol. The stock solution of polymer was prepared by dissolving 0.144 gm of polystyrene in 25 ml of solvent to get a solution with concentration  $5 \times 10^{-6}$  M.

We prepared a series of solutions containing a constant concentration of polymer  $5 \times 10^{-6}$  M and with concentrations of DEP quencher ranging from  $5 \times 10^{-5}$  M,  $7 \times 10^{-5}$  M,  $1 \times 10^{-4}$  M,  $3 \times 10^{-4}$  M to  $5 \times 10^{-4}$  M.


### 3. Results and Discussion

In this paper, we concentrate on describing the absorption and fluorescence spectra of polystyrene solutions by addition of different molecular concentrations of the quencher Diethyl phthalate (DEP) with different solvents at room temperature. Figure-1 illustrated absorption spectra of PS with different solutions of DEP ( $5 \times 10^{-5}$  M,  $7 \times 10^{-5}$  M,  $1 \times 10^{-4}$  M,  $3 \times 10^{-4}$  M  $5 \times 10^{-4}$  M) in Chloroform. It causes the appearance of a strong absorption band at 262 nm and the absorption intensity increases when the concentration of the quencher is increased. All the absorption bands occur due to  $\pi - \pi^*$  transitions.

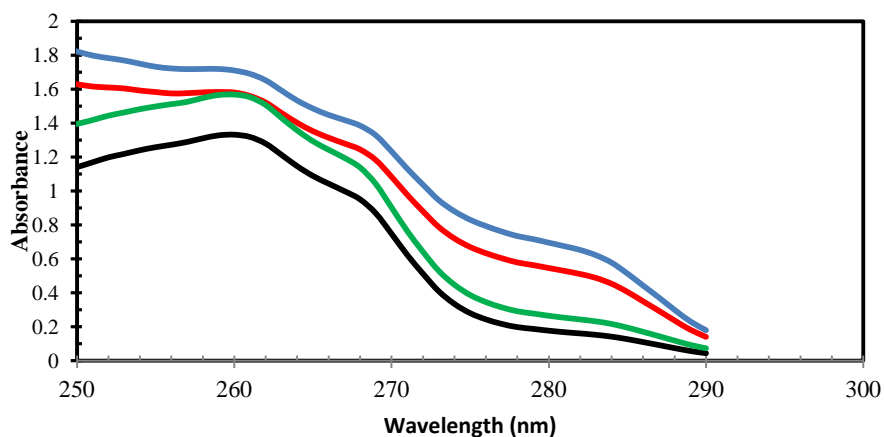


**Figure 1**-The absorption spectrum of polystyrene at different concentrations of DEP (1)  $5 \times 10^{-4}$  M, (2)  $3 \times 10^{-4}$  M, (3)  $5 \times 10^{-5}$  M, (4)  $1 \times 10^{-4}$  M in Chloroform

Figure-2 also indicated absorption spectra of polystyrene in Cyclohexane using same concentrations which were mentioned in the preceding paragraph. The characteristic of the absorption bands is weak broad symmetrical absorption bands, structureless even at low concentration.

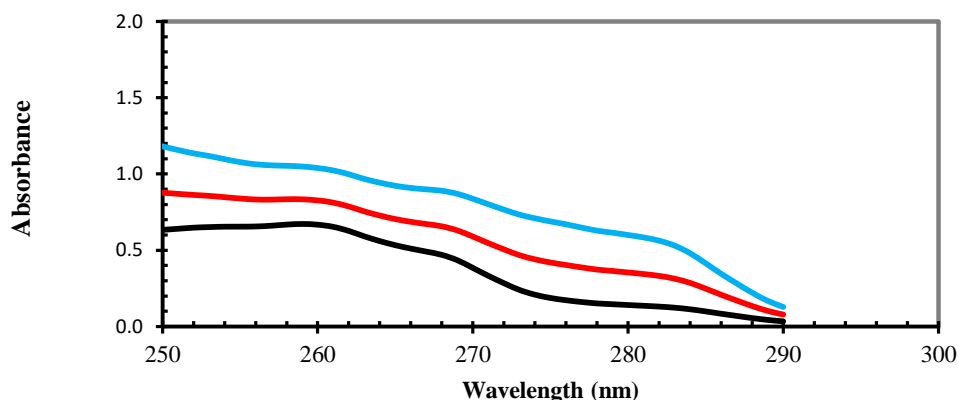


**Figure 2**-The absorption spectrum of polystyrene at different concentrations of DEP (1)  $5 \times 10^{-4}$  M, (2)  $3 \times 10^{-4}$  M,  $1 \times 10^{-4}$  M in Cyclohexane

Figures-(3, 4) represent the absorption spectra in dichloromethane and tetrahydrofuran, which are approximately symmetrical in shape, varying in the intensity of the maximum absorption package at wavelength 262 nm. It is found that the intensities and the behavior of the absorption curves are usually modified [14].

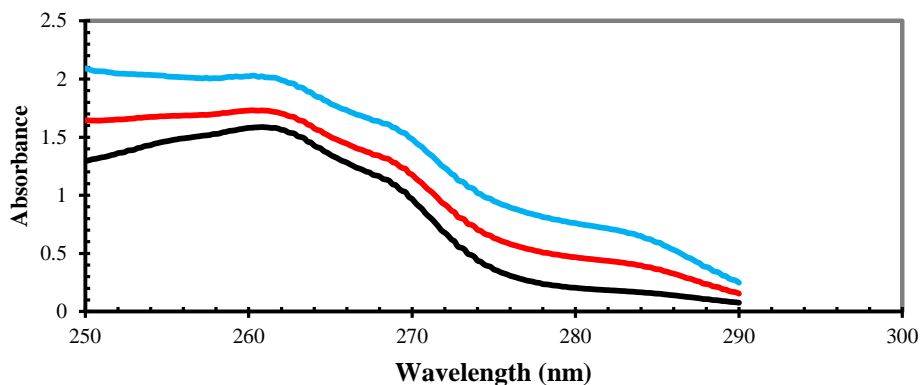


**Figure 3-**The absorption spectrum of polystyrene at different concentrations of DEP (1)  $5 \times 10^{-4}$  M, (2)  $3 \times 10^{-4}$  M, (3)  $1 \times 10^{-4}$  M in Dichloromethane

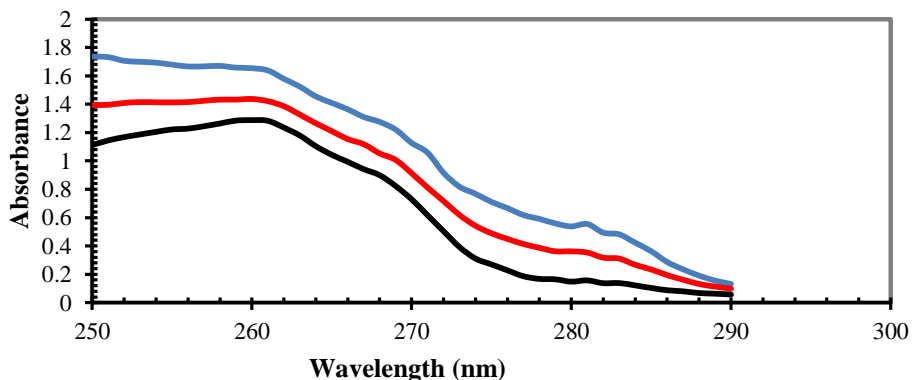


**Figure 4-**The absorption spectrum of polystyrene at different concentrations of DEP (1)  $5 \times 10^{-4}$  M, (2)  $3 \times 10^{-4}$  M, (3)  $1 \times 10^{-4}$  M in Tetrahydrofuran

In another meaning, the maximum band absorption is found to be highly dependent on solvent and quencher concentration. Figure-5 represents the fluorescence emission spectra of the polymer in the chloroform solution, in the absence of a quencher a monomer emission was observed at a 295 nm. The significant spectral broadening in the emission spectra as well as a dramatic reduction in the efficiency of emission spectra indicative of the strength of the effect of the quenching.

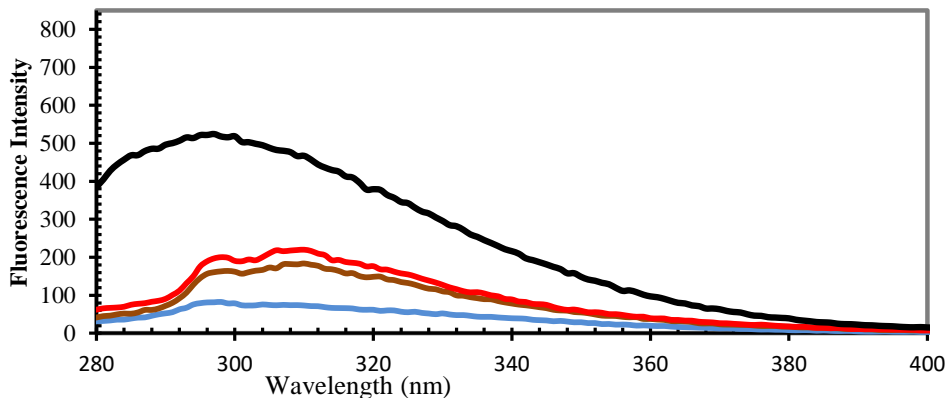


**Figure 5-**Fluorescence of polystyrene at different concentrations of DEP (1) 0M, (2)  $7 \times 10^{-5}$  M, (3)  $3 \times 10^{-4}$  M, (4)  $5 \times 10^{-4}$  M in Chloroform

It was shown during this work that in Cyclohexane and Dichloromethane the monomer and excimer emission are determined at 295 and 328 nm respectively. The experimental results in Figures- (6, 7) indicated that the most intensity of the monomer and excimer of vinyl-ring polymer solutions were clearly affected with the concentration of the quencher and the nature of the solvent.

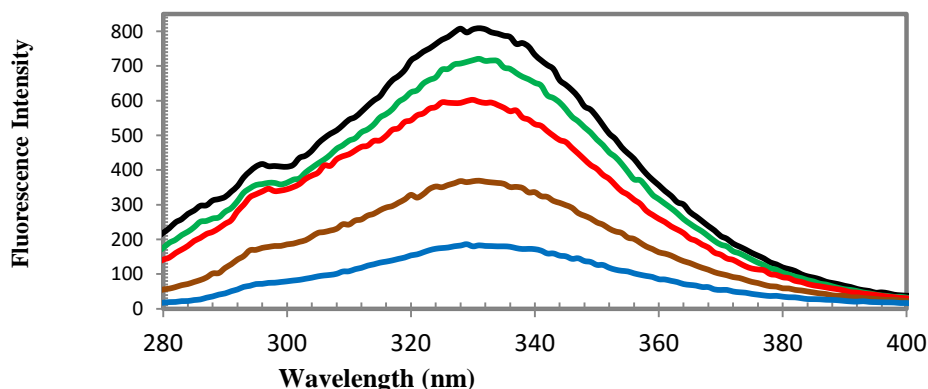


**Figure 6**-Fluorescence of polystyrene at different concentrations of DEP; (1)0M, (2) $5 \times 10^{-5}$ M, (3) $7 \times 10^{-5}$ M, (4) $3 \times 10^{-4}$ M, (5) $5 \times 10^{-4}$ M in Cyclohexane

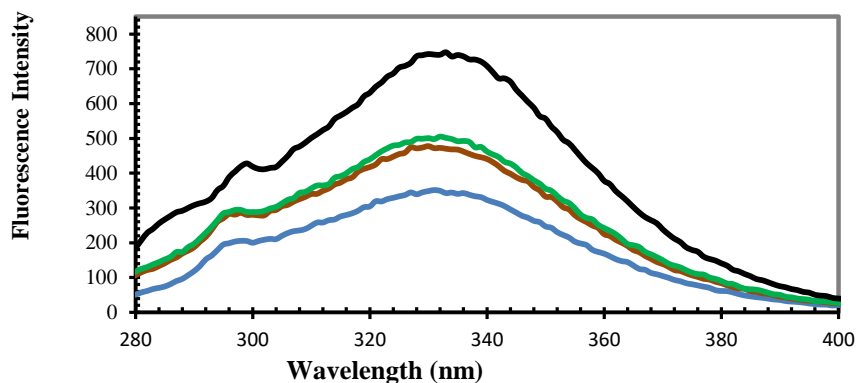

**Figure 7**-Fluorescence of polystyrene at different concentrations of DEP; (1)0M, (2) $5 \times 10^{-5}$ M, (3) $3 \times 10^{-4}$ M, (4) $5 \times 10^{-4}$ M in Dichloromethane.

The effect of solvent on the emission spectra was due to on the refractive indexes. The excimer appearance has been determined by the interaction between an excited molecule and the adjacent molecule in the same chain. Hirayama was examined the excimer formation in styrene polymer solutions at room temperature [15]. Figure-8 represents the fluorescence emission spectra in tetrahydrofuran with series DEP concentrations. The spectrum is characterized by one a broad band centered at 305 nm (excimer emission). The intensity of these bands depends on the quencher concentration because of nonradiative decay pathways [16].

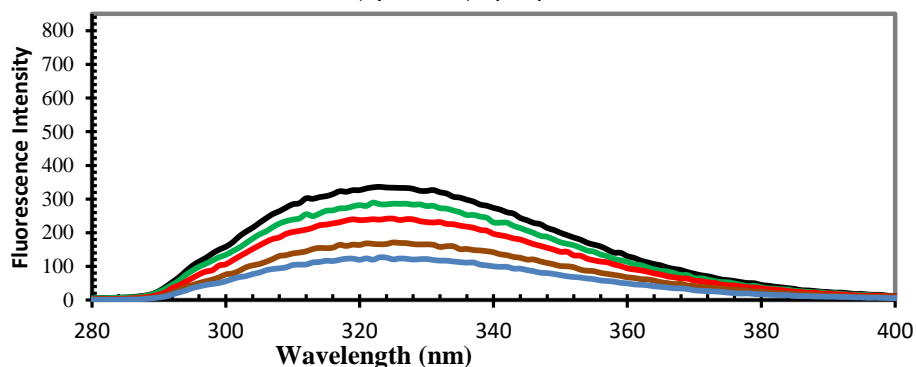

**Figure 8**-Fluorescence of polystyrene at different concentrations of DEP; (1)0M, (2) $5 \times 10^{-5}$ M, (3) $7 \times 10^{-5}$ M, (4) $3 \times 10^{-4}$ M, (5) $5 \times 10^{-4}$ M in Tetrahydrofuran

Previous relevant research has indicated that fluorescence quenching can occur by different mechanisms such as excited-state reactions, resonance energy transfer (RET), intersystem crossing, ground-state complex formation and collisional quenching [12,17]. The influence of solvent molecules on the fluorescence characteristic is certainly one of the most complex issues in fluorescence measurement. Eventually, every excited state molecule shows some dependence of its quantum yield on the chemical structure of the surrounding solvent.

This observation is to some extent due to fluorescence quenching by the solvent [18]. This quenching is due to the prompt of non-radiative transitions by changing in the energy level of the ground state, singlet excited state as well as the triplet state [19].

In this work, the decreasing in the fluorescence intensity occurs by collisional quenching. Through this process, the excited state of the molecule is returned to the ground state throughout a close encounter with the quencher. The dynamic quenching agent provides a nonradiative route for loss of the excited state energy [12, 20].

#### 4. Conclusion

In this paper, we have displayed an experimental study to describe the photophysical processes of polystyrene -Diethyl phthalate solutions. Absorption and emission spectra of PS-DEP are recorded in solvents of various polarities. The Results demonstrated that the intensity of the absorption band occurs at 262 nm increases with increasing DEP concentrations.

We observed two emission bands at 295 and 328 nm, which belong to the monomer and excimer respectively. The emission spectrum of the polymer with various concentrations of Diethyl phthalate contains one broad emission band, the excimer at 325 nm, whose intensity decreases by increasing the concentration of the quencher.

Emission Spectra of the Polystyrene with the quencher in the cyclohexane and in Dichloromethane have two emission bands, the first around 295 nm attributed to monomer emission while the second band at 328 nm to excimer emission, because of a dimer formed between chromophores on a similar polymer chain [21]. The fluorophore molecule is quenched by the interaction with the surrounding solvent molecules or by the nonradiative process (internal conversion) in which the excitation energy is converted into heat. The fluorescence quenching becomes concentration-dependent due to the collisional quenching between a singlet excited state of fluorophore and quencher molecule [22].

#### Acknowledgment

I would like to thank the Department of Applied Sciences at the University of Technology for providing practical research materials and equipment. I thank the branch of applied chemistry for contributing to the presentation of chemical and devises materials

#### References

1. Snyder, J., Grüniger, P., Bettinger, H. and Bragg, A. **2017.** " Excited-State Deactivation Pathways and the Photocyclization of BN-Doped Polyaromatics" *J. Phys. Chem.A.*, **121**(27): 5136-5146. DOI: 10.1021/acs.jpca.7b04878
2. Schnabel, W. **2007.** "*Polymers and Light, Fundamentals and Technical Applications*" WILEY-VCH Verlag GmbH & Co. KGaA,
3. Stumpe J. and Schwetlick K. **1987.** " Deactivation of Excited States in Polyurethanes by Energy Transfer to Salicylic Acid Derivatives and its Application to the Photo-stabilisation of Polyurethanes" *Polymer Degradation and Stability*, **17**: 103-115. [doi.org/10.1016/0141-3910\(87\)90098-X](https://doi.org/10.1016/0141-3910(87)90098-X)
4. Peak, D., Werner, T. C, Richard D., James B. **1983.** "Fluorescence quenching at high quencher concentrations" *J. Chem. Phys.*, **79**: 3328-3335. doi:10.1063/1.446234.
5. Chaichi M. J., Alijanpour S.O. **2014.** " The fluorescence Quenching Study of Quinine in Presence of Some Anions" *Caspian J. Chem.*, **3**(1):5-21.
6. Thomas S., Joly G. and Swage T. **2007.** " chemical sensors based on amplifying fluorescent conjugated polymers" *Chem. Rev.*, **107**(4): 1339–1386. **doi:** 10.1021/cr0501339.
7. Chikkur G. C. and Hanagodimath, S. M. **1989.** "Verification of semiempirical formulae for a ray absorption coefficient " *J. of Pure & Appl. Phys.*, **27**: 132 -133.
8. Hanagodimath, S. M. and Gadagimath, G. S. **1997.** "Role of energy migration in an organic liquid scintillator. " *Asian J. of Physics.* **6**(3): 459-465.

9. Behera, P. K., Mukherjee, T. and Mishra A. K. **1995**. "Simultaneous presence of the static and dynamic component in the fluorescence quenching for substituted naphthalene—CCl<sub>4</sub> system " *J. Lumin.*, **65**(3): 131-136. doi.org/10.1016/0022-2313(95)00067-Z.
10. Swaminathan M. and Radha N. **2004**. " The Static and dynamic model for 4-aminodiphenyl fluorescence quenching by carbon tetrachloride in hexane" *Spectrochim. Acta Part A.*, **60**: 1839-1843. doi.org/10.1016/j.saa.2003.10.001.
11. Rohtgi K.K. **1986**. "*Fundamentals of Photochemistry*", Wiley Eastern Ltd., India.
12. Lakowicz J. **2006**. "Principles of Fluorescence Spectroscopy" Springer Science, NY, USA.
13. Esam, A. Tawfiq and Shams. M. Abdul kareem, **2018**. "Effect of Temperature and Concentration on the Optical Properties of PVC Solutions" *Engineering and Technology Journal*, Vol36, Part B. No. 2: 170-174. DOI: <http://dx.doi.org/10.30684/etj.36.2B.14>
14. Reichardt C., Asharin S., Blum A., Eschner M., Mehranpour A, Milart P., Neim T., Schafer G. and Wilk M. **1993**. "Solute/solvent interactions and their empirical determination by means of solvatochromic dyes" *Pure & Appl. Chem.*, **65**(12): 2593–2601. [doi.org/ 10.1351 /pac199365122593](https://doi.org/10.1351/pac199365122593).
15. Hirayama F. **1963**. "Energy Transfer and Quenching in Plastic Scintillators" Thesis, University of Michigan.
16. Prieto I., Teetsov J., Anne M., Vanden D., and Bard A. **2001**. "A study of excimer emission in solutions of Poly (9,9-dioctylfluorene) using electrogenerated chemiluminescence," *J. Phys.Chem.A.*, **105**(3): 520–523. DOI: 10.1021/jp003566i.
17. Sánchez M. G., Laurenti M., J. Retama, Cabarcos E. and Valero E. **2016**. " Searching for the Fluorescence Quenching Mechanism of Conjugated Polymers by Cytochrome c" *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, **510**(5): 300-308. doi.org/ 10.1016/ j. colsurfa.2016.05.082.
18. Gauglitz G. and Vo-Dinh T. **2003**" *Handbook of Spectroscopy*" Wiley-Vch Verlag GmbH & Co. KGaA, Weinheim.
19. Schlag E. W., Schneider S., and Fischer S. F. **1971**. " lifetimes in excited states " *Annu.Rev. Phys. Chem.*, **22**(1): 465-526. DOI: 10.1146/annurev.pc.22.100171.002341.
20. Eftink M. And Ghir C. **1981**." Fluorescence Quenching Studies with Proteins" *Analytical Biochemistry*, **114**: 199-227. doi.org/10.1016/0003-2697(81)90474-7.
21. Odani H. **1973** ." Excimer Formation in Solutions of Vinylaromatic Polymers" *Bull. Inst. Chem. Res.*, **51**(6): 351-372. doi.org/[hdl.handle.net/2433/76511](https://hdl.handle.net/2433/76511)
22. Gong A. and Zhu X. **2013**. "Determination of epristeride by its quenching effect on the fluorescence of L-tryptophan" *J. Pharmaceutical Analysis*, **3**(6): 415-420. [doi.org/ 10.1016/ j.jpha.2013.05.001](https://doi.org/10.1016/j.jpha.2013.05.001)